



ELSEVIER

Journal of Alloys and Compounds 302 (2000) 258–260

Journal of
ALLOYS
AND COMPOUNDS

www.elsevier.com/locate/jallcom

Steady concentration distribution of hydrogen in elastic membranes during hydrogen diffusion

Wu-Shou Zhang^{a,b,*}, Xin-Wei Zhang^b, Zhong-Liang Zhang^a

^aInstitute of Chemistry, Chinese Academy of Sciences, P.O. Box 2709, Beijing 100080, People's Republic of China

^bInstitute of Applied Physics and Computational Mathematics, P.O. Box 8009, Beijing 100088, People's Republic of China

Received 28 June 1999; accepted 9 December 1999

Abstract

A critical discussion on non-linear steady-state concentration profiles for hydrogen diffusion in elastic metallic membranes, proposed by other authors, is provided based on mathematical analysis and numerical simulation. It is shown that the non-linear distribution is non-existent and the linear form is the only solution for the ideal solid solution phase. © 2000 Elsevier Science S.A. All rights reserved.

Keywords: Stress-induced diffusion; Hydrides; Bulk diffusion; Thin films

Along with the discovery of up-hill diffusion effect in hydrogen permeable metals by Lewis et al. [1], there has been much theoretical work concentrated on the aspects of stresses induced by hydrogen (interstitial) diffusion in metals (solids) [2–13]. In the field, an interesting phenomenon, which has given rise to much controversy, is the steady-state concentration distribution of hydrogen in diffusion membranes for the ideal solid solution of hydrogen in metals [2,6–12]. Li [2] and Baranowski [9] predicted that a linear form is the natural result. Furthermore, Baranowski [10] proved that the linear solution is in favor of the minimum entropy production principle. Nevertheless, Kandasamy [6] proposed the existence of non-linear distribution and it was verified by numerical simulation performed by Simon and Grzywna [11]. Moreover, Kandasamy [8] considered a quadratic profile to fit the non-linear solution but it was later criticized by Simon [12], although the same conclusion has been obtained by Baranowski [10] as early as 1992. What causes the confusion is that some experimental results [14–20] support the concept of non-linear distribution. So the steady distribution of hydrogen concentration in elastic membranes becomes a problem that needs to be clarified further.

In this note, we will prove that the linear profile of

hydrogen concentration is the only solution under steady-state diffusion using the analytical and numerical method. The non-linear form put forward by other authors [6,7,11,12] is unrealistic and the corresponding experimental evidences [14–20] are ambiguous.

Similar to the model and assumption used in previous papers [2–13], we consider hydrogen diffusion across a thin plate that allows our analysis to be reduced to a one-dimensional problem (Fig. 1). Hydrogen permeation flux for the dilute solid solution phase of hydrogen in the metal has the form [3–12]:

$$J = -DC_0(1 + u_\sigma x) \frac{\partial x}{\partial z} - DC_0 A(t) u_\sigma \frac{x}{L} \quad (1)$$

with

$$u_\sigma = \frac{2V_H^2 Y C_0}{3RT} \quad (2)$$

and

$$A(t) = -\frac{12}{L^2} \int_0^L x(z - L/2) dz \quad (3)$$

where D is the hydrogen diffusion coefficient; x is atomic ratio of hydrogen to metal atoms; C_0 is the hydrogen concentration when $x = 1$; L is the thickness of the plate; z is the coordinate along the diffusion direction; the up-stream side is $z = 0$ and the downstream side is $z = L$; V_H is

*Corresponding author. Fax: +86-10-6255-9373.

E-mail address: wszhang@a-1.net.cn (W.-S. Zhang)

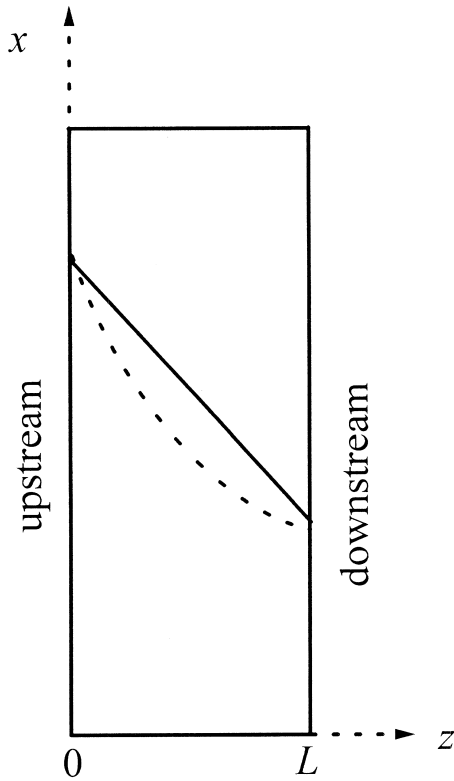


Fig. 1. Schematic picture of hydrogen diffusion across a metallic membrane. x is atomic ratio of hydrogen to metal atoms. The linear distribution is predicted by Li [2] and Baranowski [9,10], and verified by the present authors whereas the non-linear form is proposed by Kandasamy [6,7] and Simon and Grzywina [11,12].

the partial molar volume of hydrogen in the metal; $Y = E/(1 - \nu)$, E is Young's modulus; ν is Poisson's ratio; R is the molar gas constant; T is the temperature in K. Strictly speaking, x in Eq. (3) should be replaced by the difference between x and its homogeneous initial value x_0 , although the latter contributions cancel each other.

Applying the mass balance condition to the flux expression, one obtains [7–12]:

$$\frac{\partial x}{\partial t} = D(1 + u_\sigma x) \frac{\partial^2 x}{\partial z^2} + Du_\sigma \left(\frac{\partial x}{\partial z} \right)^2 + \frac{DA(t)u_\sigma}{L} \frac{\partial x}{\partial z} \quad (4)$$

with the boundary condition [9,11].

$$\frac{x}{x^*} = \exp \left\{ -u_\sigma \left[x - \frac{1}{L} \int_0^1 x dz + \frac{A(t)}{L} (z - L/2) \right] \right\}, \quad (5)$$

$z = 0 \text{ or } L$

where x^* is the value of x at the outer-surfaces corresponding to the imposed hydrogen pressure (for gas phase technique) or the applied potential (for electrolytic technique) under the stress free condition.

Firstly, we attempt to solve Eq. (1) analytically for the steady-state diffusion. Because $A(t)$ and J are all time independent in this case, Eq. (1) is reduced to an ordinary differential equation and x is uniquely determined by z . By

the assumption that $x = x_R$ at $z = L$, integrating Eq. (1) by separation of variables leads to:

$$A^2(1 - z/L) = A(x - x_R) + \frac{(A - LJ/DC_0)}{u_\sigma} \ln \left(\frac{LJ/DC_0 + Au_\sigma x}{LJ/DC_0 + Au_\sigma x_R} \right) \quad (6)$$

For extracting A , we first prove that $A > 0$. Eq. (3) may be transformed into the form:

$$A = \frac{12}{L^2} \int_0^{L/2} [x(z) - x(1 - z)](L/2 - z) dz \quad (7)$$

Because $x(z)$ decreases monotonically with the increase of z at present, there is $x(z) - x(1 - z) > 0$, when $0 \leq z < L/2$, hence $A > 0$.

Integrating Eq. (6) with a weight factor $-12(z - L/2)/L^2$ over the range $0 \leq z \leq L$, the contributions originating from $A^2(1 - z/L)$ and $A(x - x_R)$ cancel each other. This leads to:

$$(A - LJ/DC_0) \int_0^L \ln \left(\frac{LJ/DC_0 + Au_\sigma x}{LJ/DC_0 + Au_\sigma x_R} \right) (L/2 - z) dz = 0 \quad (8)$$

Because $A > 0$ and x decreases with z , it is easy to find that the logarithm function in Eq. (8) decreases monotonically with z . We can prove that the integration is larger than zero in much the same way as that for A in Eq. (7). This means that $A = LJ/DC_0$ is the only root of this equation. From Eq. (6), we obtain easily:

$$x - x_R = \frac{LJ}{DC_0} (1 - z/L) \quad (9)$$

This is exactly the linear distribution expected. Furthermore, $x = x^*$ can be derived from Eq. (5), which reveals that the self-stress is released completely as predicted by Li [2] and Baranowski [9,10].

On the other hand, we can solve Eq. (4) numerically with the boundary condition of Eq. (5) and the initial conditions. For example, we choose as boundary conditions $x^* = 0.2$ at $z = 0$ and $x^* = 0.1$ at $z = L$, and as initial condition $x_0 = 0.1$ at $0 \leq z \leq L$. This choice is similar to that of Simon and Grzywina [9], i.e. the hydrogen concentration at the upstream side increases two-fold at $t = 0$. The space-time variation of hydrogen concentration is shown in Fig. 2, the prominent decrease of hydrogen concentration near $z = L$ at initial short times can be seen as described before [6–11]. When $Dt/L^2 = 1/2$, the distribution of hydrogen apparently approaches the linear profile, as expected. In the calculation, the parameter $u_\sigma x_0$ is 0.5, being much greater than that adopted by Simon and Grzywina [11]. They concluded that there will be an opposite flux in the plate besides the concave distribution of hydrogen when $u_\sigma x_0 >$

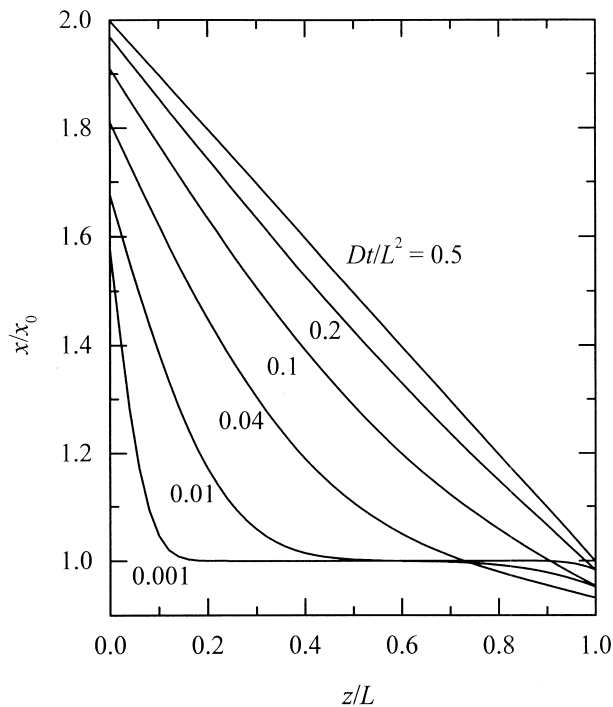


Fig. 2. Space–time variation of hydrogen concentration in a thin diffusion membrane. The parameters: $u_{\sigma}x_0 = 0.5$; boundary conditions: $x^* = 0.2$ at $z=0$ and $x^* = 0.1$ at $z=L$; initial condition: $x_0 = 0.1$ at $0 \leq z \leq L$.

0.02. But our results give neither the non-linear distribution nor an opposite flux.

Eq. (9) and Fig. 2 show clearly that the linear profile of hydrogen in the plate is the only solution for the steady-state diffusion. Any non-linear solution is either erroneous or inconsistent. For example, Kandasamy [7] has predicted a quadratic form of non-linear distribution. As predicted by Baranowski [10] and Simon [12] this form will induce the flux and concentration change with location and this is in conflict with the assumption of a steady state. On the other hand, it is hard to imagine that this non-linear function, even much more complicated, cannot be expanded in Taylor's series if it indeed exists. Our results also indicate that determination of the diffusion coefficient by the relation $D = LJ/\Delta C$ (ΔC is the concentration difference between these at two sides) is valid and it is independent of whether self-induced stress is involved or not. Of course, this theoretical prediction may face difficulties in experiments due to the complex factors involved [21].

In some experiments [14–20], there are indirect evidences that support the concept of non-linear distribution

of hydrogen concentration in plates at steady state. However, our results indicate that these complex phenomena cannot be understood by the simply picture and there must be other factors that have not been considered being concerned.

Acknowledgements

The work is supported by the Pan-Deng Project of the Department of Science and Technology of China under Grant No. 95-yu-41, the Natural Science Foundation of China and the Foundation of the China Academy of Engineering Physics. We are grateful to Professor F.A. Lewis for providing reprints.

References

- [1] F.A. Lewis, J.P. Magennis, S.G. McKee, P.J.M. Seebuwufu, *Nature* 306 (1983) 673.
- [2] J.C.M. Li, *Metall. Trans. A* 8 (1978) 1353.
- [3] F.C. Larché, J.W. Cahn, *Acta Metall.* 30 (1982) 1835.
- [4] F.C. Larché, J.W. Cahn, *Solid State Phenom.* 34 (1988) 205.
- [5] F.C. Larché, J.W. Cahn, *Acta Metall.* 40 (1992) 947.
- [6] K. Kandasamy, *Scripta Metall.* 22 (1988) 479.
- [7] K. Kandasamy, *Int. J. Hydrogen Energy* 20 (1995) 455.
- [8] K. Kandasamy, F.A. Lewis, *Defect Diffusion Forum* 150–151 (1997) 56.
- [9] B. Baranowski, *J. Less-Common Metals* 154 (1989) 329.
- [10] B. Baranowski, *Flow, diffusion and processes*, in: S. Sieniutycz, P. Salaman (Eds.), *Advances in Thermodynamics*, Vol. 6, Taylor and Francis, New York, 1992, p. 168.
- [11] A.M. Simon, Z.J. Grzywna, *Acta. Metall. Mater.* 40 (1992) 3465.
- [12] A.M. Simon, *Int. J. Hydrogen Energy* 22 (1997) 27.
- [13] P. Zoltowski, in: *Proc. of 4th Int. Symp. on Electrochemical Impedance Spectroscopy*, 2–7 August, Rio de Janeiro, Brazil, 1998, p. 405.
- [14] Y. Sakamoto, X.Q. Tong, F.A. Lewis, *Scripta Metall. Mater.* 25 (1991) 1629.
- [15] K. Kandasamy, F.A. Lewis, J.P. Magennis, S.G. McKee, X.Q. Tong, *Z. Phys. Chem. (NF)* 171 (1991) 213.
- [16] K. Kandasamy, X.Q. Tong, F.A. Lewis, *J. Phys.: Condens. Mater.* 4 (1992) L439.
- [17] F.A. Lewis, X.Q. Tong, *J. Alloys Comp.* 179 (1992) L13.
- [18] F.A. Lewis, X.Q. Tong, K. Kandasamy, *Int. J. Hydrogen Energy* 18 (1993) 481.
- [19] F.A. Lewis, X.Q. Tong, K. Kandasamy, R.V. Bucur, Y. Sakamoto, *Thermochim. Acta* 218 (1993) 57.
- [20] X.Q. Tong, F.A. Lewis, *Int. J. Hydrogen Energy* 20 (1995) 641.
- [21] B. Baranowski, private communication.